

1,1,3,3-Tetramethylguanidinium  
dihydrogenorthophosphateA. Criado,<sup>a\*</sup> M. J. Diáñez,<sup>a</sup> S. Pérez-Garrido,<sup>a</sup> I. M. L. Fernandes,<sup>b</sup> M. Belsley<sup>b</sup> and E. de Matos Gomes<sup>b</sup><sup>a</sup>Instituto de Ciencia de Materiales de Sevilla, Departamento de Física de la Materia Condensada, CSIC – Universidad de Sevilla, Apartado 1065, 41080 Sevilla, Spain, and <sup>b</sup>Departamento de Física, Universidade do Minho, 4709 Braga, Portugal  
Correspondence e-mail: criado@cica.es


Received 2 March 2000

Accepted 5 April 2000

In the title compound,  $C_5H_{14}N_3^+ \cdot H_2PO_4^-$ , the cation has a central guanidinium fragment with a planar geometry, as expected for a central  $Csp^2$  atom with a small charge delocalization along the three C–N bonds. The crystal packing is governed by hydrogen bonds so that the phosphate anions are linked head to tail, forming chains running parallel to the  $c$  direction. These chains in turn are interconnected by hydrogen bonds to intermediate tetramethylguanidinium cations forming hydrogen-bonded molecular layers stacked parallel to the  $bc$  crystal planes.

## Comment

Inorganic salts of phosphoric acids form compounds that exhibit a wealth of interesting physical properties such as ferroelectricity and non-linear optical phenomena like second harmonic generation; a classical example is potassium dihydrogen orthophosphate (KDP) (Rafikovich, 1991). A general synthetic route to obtain organo-dihydrogen orthophosphate crystals has been detailed (Masse & Zyss, 1991). In all these compounds, there is an inorganic subnetwork formed by the dihydrogen orthophosphate anions ( $H_2PO_4^-$ ). When the organic species are strongly dipolar, the anion sublattice is

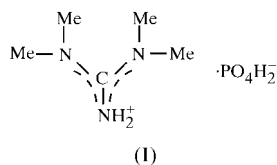

organized in a polar structure; examples are L-argininium dihydrogen orthophosphate monohydrate (Aoki *et al.*, 1971), 2-amino-5-nitropyridinium dihydrogen orthophosphate (Kotler *et al.*, 1992) and sarcosine dihydrogen orthophosphate (Averbuch-Pouchot *et al.*, 1988). In the case of a weakly dipolar organic species such as glycine, the anion sublattice will organize in a nonpolar structure (Averbuch-Pouchot *et al.*, 1988). As part of a project to study new compounds with potentially interesting optical and dielectric properties, we


have synthesized the title compound, (I). Similar to amino-guanidinium dihydrogen orthophosphate (Adams, 1977), we report here its crystal structure, as determined by single-crystal X-ray diffraction.

The compound crystallizes in a centrosymmetric space group; consequently, no non-linear optical effects are observed. Differential scanning calorimetry measurements performed from 93 to 673 K did not show any phase transition. The melting point occurs at about 493 K, followed by decomposition.

The geometry of the guanidinium group in (I) is planar, as expected for  $sp^2$  hybridization of the central C atom (Fig. 1). The  $\pi$  delocalization along the three C–N bonds gives rise to C1–N2 [1.344 (1) Å] and C1–N3 [1.346 (1) Å] bond lengths larger than the value expected for a  $Csp^2=N$  bond (1.295 Å) and close to the expected value for a delocalized C=N double bond [1.339 (5) Å]. The C1–N1 bond length [1.320 (1) Å] is somewhat shorter and compares well with the average value for the guanidinium cation (1.321 Å) (Allen *et al.*, 1987). The larger value for the C1–N2 and C1–N3 bond lengths must be ascribed to the methyl substitution which makes the three bonds non-equivalent. Indeed, simple molecular-orbital semiempirical calculations (extended Hückel) give different atomic charges on N1 (–0.376 e) and N2 and N3 (–0.590 e). As may be expected, the two P–O distances for the OH groups are significantly longer than the other two P–O distances.


The basis of the molecular engineering interest in these salts is the obtention of structures with potential physical properties as a result of the hydrogen-bond crystal network, which tends to reinforce the properties exhibited by the isolated molecule by arranging them as linear or layered molecular patterns.

In our case the hydrogen bonds also give rise to an interesting arrangement, which is best understood with the aid of the diagram corresponding to the crystal structure viewed perpendicular to the  $ab$  plane (Fig. 2). On one hand, each phosphate ion is connected by two hydrogen bonds to each phosphate ion related to it by a  $c$  glide plane with both positive and negative fractional  $c$  translations. Given that the central P atoms lie at a very close distance to the glide planes (0.32 Å), it results in approximately linear phosphate chains parallel to the  $c$  direction. On the other hand, each tetramethylguanidinium ion is hydrogen-bonded to two phosphate ions related to each other by an inversion centre and belonging to different chains, giving rise to a framework of molecules

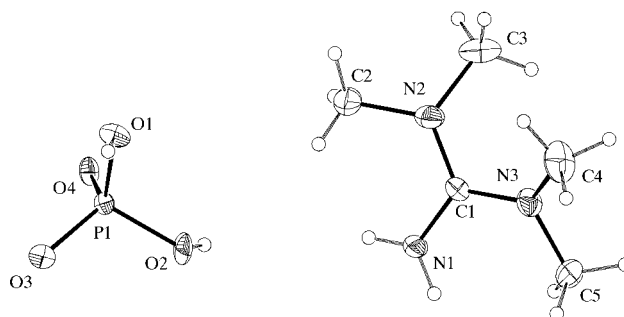

**Figure 1**  
Structure of (I) showing 30% probability displacement ellipsoids.

connected by hydrogen bonds in the form of layers parallel to the *bc* crystal planes and stacked according to the *a* lattice translation period. Besides the above, two C—H...O contacts interrelating molecules within the same layer and not depicted in the diagram have been detected.

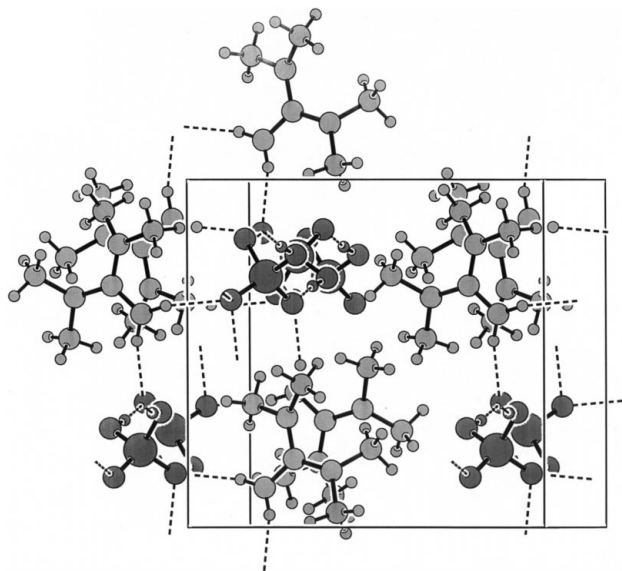

**Figure 2**  
The molecular packing viewed along an axis perpendicular to the *ab* plane showing the hydrogen bonding.

## Experimental

The title compound was prepared by mixing equimolar portions of two reagents: 1,1,3,3-tetramethylguanidine (99%) and phosphoric acid (85%) in a 1:1 solution of ethanol and water at room temperature. Good quality, colourless single crystals of prism habit were grown from the solution by slow evaporation, one of which was selected and used for the X-ray analysis.

### Crystal data

$C_5H_{14}N_3^+ \cdot H_2PO_4^-$	$D_m$ measured by flotation in bromobenzene and acetone
$M_r = 213.18$	Mo $K\alpha$ radiation
Monoclinic, $P2_1/c$	Cell parameters from 25 reflections
$a = 11.225$ (3) Å	$\theta = 7-12^\circ$
$b = 10.951$ (1) Å	$\mu = 0.264$ mm <sup>-1</sup>
$c = 8.430$ (2) Å	$T = 293$ (2) K
$\beta = 103.50$ (1)°	Prism, colourless
$V = 1007.6$ (4) Å <sup>3</sup>	$0.80 \times 0.50 \times 0.40$ mm
$Z = 4$	
$D_x = 1.405$ Mg m <sup>-3</sup>	
$D_m = 1.40$ Mg m <sup>-3</sup>	

### Data collection

Enraf–Nonius CAD-4 diffractometer	$h = 0 \rightarrow 17$
$\omega$ - $2\theta$ scans	$k = 0 \rightarrow 16$
3777 measured reflections	$l = -12 \rightarrow 12$
3777 independent reflections	3 standard reflections
3257 reflections with $I > 2\sigma(I)$	frequency: 60 min
$\theta_{max} = 32.96^\circ$	intensity decay: none

### Refinement

Refinement on $F^2$	$w = 1/[\sigma^2(F_o^2) + (0.0639P)^2 + 0.1114P]$
$R[F^2 > 2\sigma(F^2)] = 0.034$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.105$	$(\Delta/\sigma)_{max} < 0.001$
$S = 1.080$	$\Delta\rho_{max} = 0.46$ e Å <sup>-3</sup>
3777 reflections	$\Delta\rho_{min} = -0.37$ e Å <sup>-3</sup>
124 parameters	
H-atom parameters constrained	

**Table 1**

Selected geometric parameters (Å, °).

P1—O4	1.4968 (7)	N3—C5	1.461 (2)
P1—O3	1.5148 (7)	N3—C4	1.458 (2)
P1—O1	1.5629 (8)	N2—C1	1.3447 (15)
P1—O2	1.5800 (8)	N2—C3	1.466 (2)
N1—C1	1.3198 (13)	N2—C2	1.455 (2)
N3—C1	1.3451 (14)		
O4—P1—O3	114.78 (5)	C5—N3—C4	114.50 (12)
O4—P1—O1	108.64 (5)	C1—N2—C3	121.02 (12)
O3—P1—O1	109.11 (4)	C1—N2—C2	121.27 (11)
O4—P1—O2	110.24 (4)	C3—N2—C2	115.34 (12)
O3—P1—O2	108.20 (5)	N1—C1—N2	120.78 (11)
O1—P1—O2	105.47 (5)	N1—C1—N3	120.22 (10)
C1—N3—C5	120.91 (10)	N2—C1—N3	119.01 (10)
C1—N3—C4	121.53 (12)		

**Table 2**

Hydrogen-bonding geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
N1—H1A...O3	0.88	2.08	2.924 (1)	161
O2—H2...O3 <sup>i</sup>	0.84	1.79	2.616 (1)	167
O1—H1...O4 <sup>ii</sup>	0.84	1.71	2.541 (1)	169
N1—H1B...O3 <sup>iii</sup>	0.88	2.07	2.894 (1)	155
C5—H5B...O2 <sup>iii</sup>	0.98	2.56	3.521 (2)	167
C5—H5A...O2 <sup>iv</sup>	0.98	2.67	3.607 (2)	159

Symmetry codes: (i)  $x, -\frac{1}{2}-y, z-\frac{1}{2}$ ; (ii)  $x, -\frac{1}{2}-y, \frac{1}{2}+z$ ; (iii)  $-x, -y, 1-z$ ; (iv)  $x, 1+y, z$ .

Data collection and cell refinement: *CAD-4 Software* (Enraf–Nonius, 1989); data reduction: *XRAY76* (Stewart *et al.*, 1976); program(s) used to solve structure: *SIR92* (Altomare *et al.*, 1994); program(s) used to refine structure: *SHELXL93* (Sheldrick, 1993); molecular graphics: *PLATON* (Spek, 1994); software used to prepare material for publication: *PARST* (Nardelli, 1995) and *PARSTCIF* (Nardelli, 1991).

This work was supported by the Spanish CICYT project PB98-1126. We also acknowledge travel support from Accion Integrada Hispano-Portuguesa HP 1999-0070.

Supplementary data for this paper are available from the IUCr electronic archives (Reference: NA1466). Services for accessing these data are described at the back of the journal.

## References

- Adams, J. M. (1977). *Acta Cryst.* **B33**, 1513–1515.  
 Allen, F. H., Kennard, O., Watson, D. G., Brammer, L., Orpen, A. G. & Taylor, R. (1987). *J. Chem. Soc. Perkin Trans. 2*, pp. S1–19.  
 Altomare, A., Cascarano, G., Giacovazzo, C., Guagliardi, A., Burla, M. C., Polidori, G. & Camalli, M. (1994). *J. Appl. Cryst.* **27**, 435.  
 Aoki, K., Nagano, K. & Iitaka, Y. (1971). *Acta Cryst.* **B27**, 11–23.  
 Averbuch-Pouchot, A. T., Durif, A. & Guitel, J. C. (1988). *Acta Cryst.* **C44**, 99–102.  
 Enraf–Nonius (1989). *CAD-4 Software*. Version 5.0. Enraf–Nonius, Delft, The Netherlands.  
 Kotler, Z., Hierle, R., Josse, D., Zyss, J. & Masse, R. (1992). *J. Opt. Soc. Am.* **B9**, 534–547.  
 Masse, R. & Zyss, J. (1991). *Mol. Eng.* **1**, 141–152.  
 Nardelli, M. (1991). *PARSTCIF*. University of Parma, Italy.  
 Nardelli, M. (1995). *J. Appl. Cryst.* **28**, 659.  
 Raftery, L. N. (1991). *KDP-Family Single Crystals*. Bristol: IOP Publishing.  
 Sheldrick, G. M. (1993). *SHELXL93*. University of Göttingen, Germany.  
 Spek, A. L. (1994). *PLATON*. University of Utrecht, The Netherlands.  
 Stewart, J. M., Machin, P. A., Dickinson, C. W., Ammon, H. L., Heck, H. & Flack, H. (1976). *The XRAY76 System*. Technical Report TR-446. Computer Science Center, University of Maryland, USA.

## supporting information

*Acta Cryst.* (2000). C56, 888-889 [doi:10.1107/S0108270100005187]

## 1,1,3,3-Tetramethylguanidinium dihydrogenorthophosphate

A. Criado, M. J. Diáñez, S. Pérez-Garrido, I. M. L. Fernandes, M. Belsley and E. de Matos Gomes

### Computing details

Data collection: *CAD-4 Software* (Enraf-Nonius, 1989); cell refinement: *SET4* (de Boer & Duissenberg, 1984) and *CELDIM* (CAD4, Retting, 1989); data reduction: *XRAY76 System* (Stewart *et al.*, 1976); program(s) used to solve structure: *SIR92* (Altomare *et al.*, 1994); program(s) used to refine structure: *SHELXL93* (Sheldrick, 1993); molecular graphics: *PLATON* (Spek, 1994); software used to prepare material for publication: *PARST* (Nardelli, 1995) and *PARSTCIF* (Nardelli, 1991).

### 1,1,3,3-tetramethyl guanidinium phosphate

#### Crystal data

$C_5H_{14}N_3^+ \cdot H_2PO_4^-$   
 $M_r = 213.18$   
 Monoclinic,  $P2_1/c$   
 $a = 11.225$  (3) Å  
 $b = 10.951$  (1) Å  
 $c = 8.430$  (2) Å  
 $\beta = 103.50$  (1)°  
 $V = 1007.6$  (4) Å<sup>3</sup>  
 $Z = 4$   
 $F(000) = 456$

$D_x = 1.405$  Mg m<sup>-3</sup>  
 $D_m = 1.40$  Mg m<sup>-3</sup>  
 $D_m$  measured by flotation in bromobenzene and acetone  
 Melting point: 493 K  
 Mo  $K\alpha$  radiation,  $\lambda = 0.71069$  Å  
 Cell parameters from 25 reflections  
 $\theta = 7-12^\circ$   
 $\mu = 0.26$  mm<sup>-1</sup>  
 $T = 293$  K  
 Prism, colourless  
 0.80 × 0.50 × 0.40 mm

#### Data collection

Enraf-Nonius CAD4  
 diffractometer  
 Radiation source: fine-focus sealed tube  
 Graphite monochromator  
 $\omega-2\theta$  scans  
 3777 measured reflections  
 3777 independent reflections  
 3257 reflections with  $I > 2\sigma(I)$

$R_{int} = 0.000$   
 $\theta_{max} = 33.0^\circ$ ,  $\theta_{min} = 2.6^\circ$   
 $h = 0 \rightarrow 17$   
 $k = 0 \rightarrow 16$   
 $l = -12 \rightarrow 12$   
 3 standard reflections every 60 min  
 intensity decay: none

#### Refinement

Refinement on  $F^2$   
 Least-squares matrix: full  
 $R[F^2 > 2\sigma(F^2)] = 0.034$   
 $wR(F^2) = 0.105$   
 $S = 1.08$   
 3777 reflections

124 parameters  
 0 restraints  
 Primary atom site location: structure-invariant direct methods  
 Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from  
neighbouring sites  
H-atom parameters constrained

$$\begin{aligned} \text{Calculated } w &= 1/[\sigma^2(F_o^2) + (0.0639P)^2 + \\ &0.1114P] \\ \text{where } P &= (F_o^2 + 2F_c^2)/3 \\ (\Delta/\sigma)_{\max} &< 0.001 \\ \Delta\rho_{\max} &= 0.46 \text{ e } \text{Å}^{-3} \\ \Delta\rho_{\min} &= -0.37 \text{ e } \text{Å}^{-3} \end{aligned}$$

*Special details*

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement on  $F^2$  for ALL reflections except for 0 with very negative  $F^2$  or flagged by the user for potential systematic errors. Weighted  $R$ -factors  $wR$  and all goodnesses of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The observed criterion of  $F^2 > \sigma(F^2)$  is used only for calculating `R_factor_obs` etc. and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (Å<sup>2</sup>)*

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
P1	0.21200 (2)	-0.22099 (2)	0.44607 (3)	0.02297 (8)
O4	0.26662 (8)	-0.14310 (7)	0.33544 (9)	0.0318 (2)
O3	0.12944 (7)	-0.15363 (7)	0.53532 (9)	0.0296 (2)
O2	0.13625 (9)	-0.32927 (8)	0.34687 (10)	0.0384 (2)
H2	0.1421	-0.3263	0.2494	0.058*
O1	0.31819 (7)	-0.28321 (8)	0.57362 (10)	0.0348 (2)
H1	0.2919	-0.3067	0.6540	0.052*
N1	0.13166 (8)	0.11300 (8)	0.51765 (13)	0.0358 (2)
H1A	0.14840	0.03517	0.53720	0.043*
H1B	0.05591	0.13620	0.47485	0.043*
N3	0.19506 (10)	0.31397 (9)	0.52252 (13)	0.0386 (2)
N2	0.33639 (9)	0.16108 (10)	0.61799 (14)	0.0415 (2)
C1	0.22015 (10)	0.19494 (10)	0.55254 (13)	0.0309 (2)
C5	0.08049 (12)	0.35246 (12)	0.4126 (2)	0.0459 (3)
H5A	0.0924	0.4317	0.3645	0.069*
H5B	0.0166	0.3597	0.4739	0.069*
H5C	0.0556	0.2918	0.3257	0.069*
C2	0.36472 (13)	0.04187 (13)	0.6937 (2)	0.0530 (4)
H2A	0.4411	0.0469	0.7782	0.080*
H2B	0.3742	-0.0177	0.6108	0.080*
H2C	0.2979	0.0162	0.7430	0.080*
C4	0.2563 (2)	0.40878 (13)	0.6335 (2)	0.0626 (4)
H4A	0.1968	0.4485	0.6851	0.094*
H4B	0.2915	0.4695	0.5723	0.094*
H4C	0.3216	0.3721	0.7177	0.094*
C3	0.43961 (13)	0.2244 (2)	0.5750 (2)	0.0630 (5)
H3A	0.4925	0.1646	0.5386	0.094*
H3B	0.4867	0.2681	0.6707	0.094*
H3C	0.40852	0.2828	0.4870	0.094*

Atomic displacement parameters ( $\text{\AA}^2$ )

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
P1	0.02584 (12)	0.02308 (12)	0.02056 (11)	0.00027 (7)	0.00656 (8)	0.00083 (7)
O4	0.0431 (4)	0.0283 (3)	0.0264 (3)	-0.0075 (3)	0.0125 (3)	0.0006 (3)
O3	0.0303 (3)	0.0317 (3)	0.0277 (3)	0.0081 (3)	0.0087 (3)	0.0015 (3)
O2	0.0539 (5)	0.0356 (4)	0.0279 (3)	-0.0179 (4)	0.0137 (3)	-0.0048 (3)
O1	0.0294 (3)	0.0464 (5)	0.0301 (3)	0.0121 (3)	0.0100 (3)	0.0092 (3)
N1	0.0266 (4)	0.0261 (4)	0.0535 (6)	0.0007 (3)	0.0072 (4)	-0.0021 (4)
N3	0.0430 (5)	0.0271 (4)	0.0458 (5)	-0.0043 (4)	0.0105 (4)	-0.0041 (4)
N2	0.0282 (4)	0.0438 (5)	0.0496 (6)	-0.0022 (4)	0.0032 (4)	-0.0042 (4)
C1	0.0300 (4)	0.0297 (4)	0.0339 (5)	-0.0012 (3)	0.0093 (4)	-0.0058 (4)
C5	0.0426 (6)	0.0347 (6)	0.0626 (8)	0.0028 (5)	0.0168 (6)	0.0122 (5)
C2	0.0417 (6)	0.0429 (7)	0.0653 (9)	0.0081 (5)	-0.0059 (6)	-0.0054 (6)
C4	0.0952 (13)	0.0332 (6)	0.0558 (8)	-0.0164 (7)	0.0105 (8)	-0.0130 (6)
C3	0.0298 (6)	0.0859 (13)	0.0708 (10)	-0.0132 (7)	0.0071 (6)	0.0034 (9)

Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )

P1—O4	1.4968 (7)	N2—C2	1.455 (2)
P1—O3	1.5148 (7)	C5—H5A	0.98
P1—O1	1.5629 (8)	C5—H5B	0.98
P1—O2	1.5800 (8)	C5—H5C	0.98
O2—H2	0.84	C2—H2A	0.98
O1—H1	0.84	C2—H2B	0.98
N1—C1	1.3198 (13)	C2—H2C	0.98
N1—H1A	0.88	C4—H4A	0.98
N1—H1B	0.88	C4—H4B	0.98
N3—C1	1.3451 (14)	C4—H4C	0.98
N3—C5	1.461 (2)	C3—H3A	0.98
N3—C4	1.458 (2)	C3—H3B	0.98
N2—C1	1.3447 (15)	C3—H3C	0.98
N2—C3	1.466 (2)		
O4—P1—O3	114.78 (5)	H5A—C5—H5B	109.5
O4—P1—O1	108.64 (5)	N3—C5—H5C	109.47
O3—P1—O1	109.11 (4)	H5A—C5—H5C	109.5
O4—P1—O2	110.24 (4)	H5B—C5—H5C	109.5
O3—P1—O2	108.20 (5)	N2—C2—H2A	109.47
O1—P1—O2	105.47 (5)	N2—C2—H2B	109.47
P1—O2—H2	109.47	H2A—C2—H2B	109.5
P1—O1—H1	109.47	N2—C2—H2C	109.47
C1—N1—H1A	120.00	H2A—C2—H2C	109.5
C1—N1—H1B	120.00	H2B—C2—H2C	109.5
H1A—N1—H1B	120.0	N3—C4—H4A	109.47
C1—N3—C5	120.91 (10)	N3—C4—H4B	109.47
C1—N3—C4	121.53 (12)	H4A—C4—H4B	109.5
C5—N3—C4	114.50 (12)	N3—C4—H4C	109.47

C1—N2—C3	121.02 (12)	H4A—C4—H4C	109.5
C1—N2—C2	121.27 (11)	H4B—C4—H4C	109.5
C3—N2—C2	115.34 (12)	N2—C3—H3A	109.47
N1—C1—N2	120.78 (11)	N2—C3—H3B	109.47
N1—C1—N3	120.22 (10)	H3A—C3—H3B	109.5
N2—C1—N3	119.01 (10)	N2—C3—H3C	109.47
N3—C5—H5A	109.47	H3A—C3—H3C	109.5
N3—C5—H5B	109.47	H3B—C3—H3C	109.5

*Hydrogen-bond geometry (Å, °)*

<i>D</i> —H $\cdots$ <i>A</i>	<i>D</i> —H	H $\cdots$ <i>A</i>	<i>D</i> $\cdots$ <i>A</i>	<i>D</i> —H $\cdots$ <i>A</i>
N1—H1 <i>A</i> $\cdots$ O3	0.88	2.08	2.924 (1)	161
O2—H2 $\cdots$ O3 <sup>i</sup>	0.84	1.79	2.616 (1)	167
O1—H1 $\cdots$ O4 <sup>ii</sup>	0.84	1.71	2.541 (1)	169
N1—H1 <i>B</i> $\cdots$ O3 <sup>iii</sup>	0.88	2.07	2.894 (1)	155
C5—H5 <i>B</i> $\cdots$ O2 <sup>iii</sup>	0.98	2.56	3.521 (2)	167
C5—H5 <i>A</i> $\cdots$ O2 <sup>iv</sup>	0.98	2.67	3.607 (2)	159

Symmetry codes: (i)  $x, -y-1/2, z-1/2$ ; (ii)  $x, -y-1/2, z+1/2$ ; (iii)  $-x, -y, -z+1$ ; (iv)  $x, y+1, z$ .